

DEKRA Industrial GmbH Handwerkstr. 15 D-70565 Stuttgart

Kambukka bvba  
Stijn Lowette  
Torenplein 7.16.1

3500 Hasselt  
Belgium

**DEKRA Industrial GmbH**  
Laboratory for Environmental & Product Analysis  
Handwerkstr. 15  
70565 Stuttgart  
Tel. +49.711.7861-3548  
Fax +49.711.7861-3534

Contact:  
Alexandra Läßle  
Telephone 0711/7861-3576  
E-mail alexandra.laepple@dekra.com  
Date 11.05.2012  
Page 1 of 5

**Test Report No.:** 55177390/12

**Project No.:** 55177390

Client: Kambukka bvba  
Stijn Lowette  
Torenplein 7.16.1

3500 Hasselt  
Belgium

Date of order: 19.04.2012

Sample received: 20.04.2012

Number of samples: 1 sample

Article description: „Madison green“

Scope of investigation: Testing of consumer goods

Testing Period: 20.04.2012 – 11.05.2012

**Test Result:**

- following page / pages -

Accredited Analytical Laboratory D-PL-11067-02-00 in Stuttgart and Halle (Saale).

<b>Sample No.:</b>	55177390001			
<b>Sample designation:</b>	„Madison green“ (complete product)			
<b>Sample description:</b>	commodity			
<b>Parameter</b>	<b>Unit</b>	<b>Result</b>	<b>LQ</b>	<b>Method</b>
Sensorical test <sup>1,2</sup>	-	0	-	Acc. to DIN 10 955
Global migration: 3% acetic acid <sup>3</sup>	mg/dm <sup>2</sup>	0,2	0,1	Annex III of Reg. (EU)10/ 2011
Global migration: 10 % ethanol <sup>3</sup>	mg/dm <sup>2</sup>	0,8	0,1	
Primary aromatic amines <sup>4</sup>	mg/ L	< LQ	0,002	§ 64 LFGB L 00.00-6
<b>Specific migration of metals <sup>5</sup></b>				
Barium	mg/ L	< LQ	0,01	VO (EU) 10/2011 EN ISO 11885
Cobalt	mg/ L	< LQ	0,01	
Copper	mg/ L	< LQ	0,01	
Iron	mg/ L	< LQ	0,01	
Lithium	mg/ L	< LQ	0,01	
Manganese	mg/ L	< LQ	0,002	
Zinc	mg/ L	< LQ	0,01	

<sup>1</sup> Scale of intensity

- 0 - no noticeable change of smell and taste
- 1 - marginal change of smell and taste
- 2 - slight change of smell and taste
- 3 - clear change of smell and taste
- 4 - strong change of smell and taste

<sup>2</sup> Testing conditions:  
sample was filled with hot (boiling) water, sample stood 24 h with closed lid (turned upside down)


<sup>3</sup> Testing conditions:  
sample was filled with hot (boiling) simulant, sample stood 24 h with closed lid (turned upside down)

<sup>4</sup> Testing conditions:  
sample was filled with hot (boiling) 3 % acetic acid, sample stood 24 h with closed lid (turned upside down);  
not accredited test method

<sup>5</sup> Testing conditions:  
sample was filled with hot (boiling) 3 % acetic acid, sample stood 24 h with closed lid (turned upside down)

<b>Sample No.:</b>	55177390002			
<b>Sample designation:</b>	„Madison green“ (plastic material)			
<b>Sample description:</b>	commodity			
<b>Parameter</b>	<b>Unit</b>	<b>Result</b>	<b>LQ</b>	<b>Method</b>
<b>Heavy metals – mixed sample (green and white plastic material of lid and bottle)</b>				
Cadmium	mg/kg	< LQ	2	EN ISO 11885
Lead	mg/kg	< LQ	10	

**Product foto:**

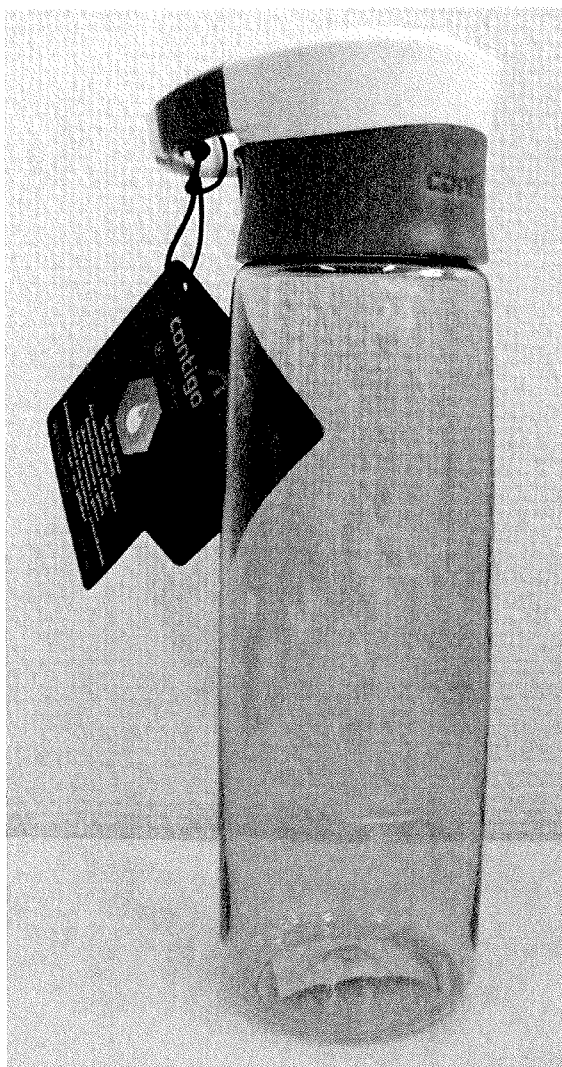

**Resume:**

According to §2 subsection 6 no.1 of the German Food and Feed Code (LFGB) the tested sample is a food contact article.

According to article 3 subsection 1 c of the regulation (EC) 1935/2004 materials and articles shall be manufactured in compliance with good manufacturing practise so that, under normal or foreseeable conditions of use, they do not transfer their constituents to food in quantities which could bring about a deterioration in the organoleptic characteristics thereof.  
The tested sample meets this requirement.

The sample meets the limit values for the migration of metals according to annex II of the Regulation (EU) 10/2011 on plastic materials and articles intended to come into contact with food.

According to article 10 combined with annex II of the regulation (EU) 10/2011 plastic materials and articles shall not release primary aromatic amines in a detectable quantity into food or food stimulant (detection limit is 0,01 mg per kg of food or food stimulant).  
The tested extract of the tested sample meets this requirement.

According to article 12 (1) of the regulation (EU) 10/2011 plastic materials and articles shall not transfer their constituents to food simulants in quantities exceeding 10 milligrams per dm<sup>2</sup>.  
The sample keeps this limit for all tested simulants.

In the mixed samples no Cadmium and Lead were detected.

**Hints:**

The test results refer exclusively to the samples specified. A reproduction in excerpts of the test report must not be made without the written consent of the test laboratory. Samples will be stored according to QMH 2001.5.8 for max. 6 months (for exceptions and specific storage times see QMH 2001.5.8). This test report replaces the test report of the same Project number with an index reduced by 1.

Stuttgart, 2012/05/11

**DEKRA Industrial GmbH**  
Laboratory for Environmental and Product Analysis

